



**EKOTEKS LABORATUVAR ve GÖZETİM  
HİZMETLERİ A.Ş.**

Esenyurt Firuzköy Bulvarı No:29 34325 Avcılar  
İstanbul/ TÜRKİYE

**TEST REPORT**  
*DENEY RAPORU*

20015708-  
ing

05-20

**Customer name:** UNIVERSAL SERTİFİKASYON VE GÖZETİM HİZMETLERİ TİCARET LTD.ŞTİ.  
**Address:** 15 Temmuz Mah. Gülbahar Cad. No:96 Bağcılar/İSTANBUL  
**Buyer name:** KIRANN KURUMSAL TEKSTİL SAN. DIŞ TİC. LTD.ŞTİ.  
**Contact Person:** SUAT KAÇMAZ  
**Order No:** -  
**Article No:** -  
**Name and identity of test item:** Blue surgical gown.  
**The date of receipt of test item:** 18.05.2020  
**Re-submitted/re-confirmation date:** -  
**Date of test:** 18.05.2020-21.05.2020  
**Remarks:** -  
**Sampling:** The results given in this report belong to the received sample by vendor.  
**End-Use:** -  
**Care Label:** Not specified.  
**Number of pages of the report:** 6

Seal

Date  
21.05.2020

Customer Representative  
SERVİN YURTSEVEN

Head of Testing Laboratory  
Sevim A. RAZAK  
21.05.2020

This report shall not be reproduced other than in full except with the permission of the laboratory.  
Testing reports without signature and seal are not valid.


**EKOTEKS LABORATUVAR ve GÖZETİM  
HİZMETLERİ A.Ş.**

20015708-  
ing

05-20

REQUIRED TESTS	RESULT	COMMENTS
<b>MICROBIOLOGICAL TEST/</b>		
Microbial Cleanliness (Bioburden)	P	
Wet-Bacterial Penetration	P	
<b>PHYSICAL PROPERTIES TESTS</b>		
Tensile Strength / Dry	P	
Tensile Strength / Wet	P	
Bursting Strength / Dry	P	
Bursting Strength / Wet	P	
P: Pass F: Fail R: Refer to retailer technologist. Test results were evaluated according to EN 13795-1:2019 Standard Performance Properties Critical Sample Group limit values (Table 1)		

REMARK: Original samples are kept for 3 months and all technical records are kept for 5 years unless otherwise specified. If requested, measurement uncertainty will be reported. But unless otherwise specified, measurement uncertainty is not considered while stating compliance with specification or limit values. The reported uncertainty is based on a standard uncertainty multiplied by a coverage factor  $k=2$ , providing a level of confidence of approximately 95 %. Tests marked (\*) in this report are not included in the accreditation schedule.

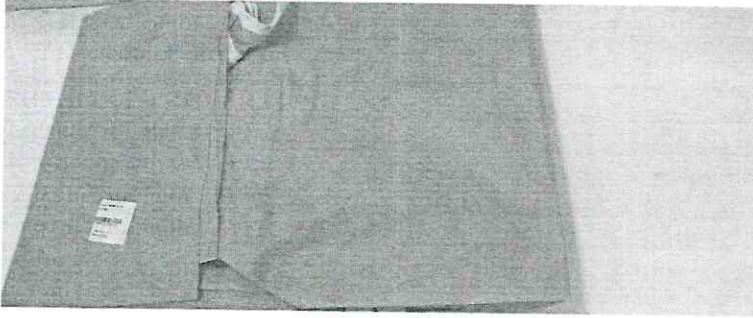

This report shall not be reproduced other than in full except with the permission of the laboratory.  
*Testing reports without signature and seal are not valid.*

20015708-  
ing

05-20

## TEST RESULTS

### MICROBIAL CLEANLINESS (Bioburden)

Test Metod: Ref: EN ISO 11737-1:2018 (\*)

The sample is put in extraciton liquid after shaking well, inoculated on the agar.  
After incubation at  $30 \pm 1$  ° C for 72 hours, growth microorganisms are counted on the agar.

	<u>RESULTS</u>	<u>REQUIREMENT</u>
Microbial cleanliness (cfu/g)	203 cfu/100 cm <sup>2</sup>	≤300 cfu/100 cm <sup>2</sup>

\*cfu= Colony forming unit.



**EKOTEKS LABORATUVAR ve GÖZETİM  
HİZMETLERİ A.Ş.**

20015708-  
ing

05-20

## TEST RESULTS

**Test Method:** BS EN 22610: 2006 (Surgical drapes, garments and fresh air clothes used as medical devices for patients, hospital staff and equipment - Test method for determination of resistance to wet bacterial permeability) (\*)

A test sample is placed on the agar plate on a rotating disc. Bacteria carrier material and coating film are placed on the test sample and all parts are fixed on the disk. A finger is placed on the test sample to apply a certain force ( $3N \pm 0.02$ ). The finger moves on the test sample over the entire surface of the agar within 15 minutes. 5 studies are carried out for 15 minutes. 6. The study is repeated by inverting the sample.

Sample amount:	5 pieces 25x25cm2
Carrier Material:	30 µm thin, 25x25cm2 Polyurethane Film
Coating Material:	25x25cm2 HDPE Film
Microorganism:	Staphylococcus aureus ATCC 29213
Bacterial Concentration (kob / ml):	1-4x104 kob / ml
Incubation Conditions:	(36 ± 1) ° C 48 hours

RESULTS			
Number of Populating Bacteria (cfu)		Penetration Rate	
X1	228	RCUM1	0,18
X2	220	RCUM2	0,36
X3	229	RCUM3	0,54
X4	220	RCUM4	0,72
X5	112	RCUM5	0,81
Z	234		
T	1243		
X1 ..... X5: Number of colonies growing in 5 parallel petri in the same sample Z: number of colonies growing in the sixth petri dish T: X1 + X2 + X3 + X4 + X5 + Z  RCUM1 = X1/T RCUM2 = (X2 + X1)/T RCUM3 = (X3 + X2 + X1)/T RCUM4 = (X4 + X3 + X2 + X1)/T RCUM5 = (X5 + X4 + X3 + X2 + X1)/T			
BARRIER INDEX (IB )			
	Result	Expected value (*)	
IB	3,38	≥2,8	
IB = 6 – (CUM1 + CUM2 + CUM3 + CUM4 + CUM5)			
* EN 13795-1:2019 Surgical gowns and drapes - Requirements and test methods are evaluated according to Table-1.			

Gen.fl136-2/03

20015708-  
ing

05-20

## TEST RESULTS

TEST METHOD : EN 13795-1:2019

SURGICAL CLOTHING AND DRAPES –REQUIREMENTS AND TEST METHODS

ANNEX 1: SURGICAL CLOTHING AND DRAPES (\*);

### TENSILE STRENGTH; EN 29073-3:1996 (\*)

Instron 5969 (Load: 50 kN), Strip Method.  
Speed: 100 mm/min $\pm$ 10, Gauge length 200 mm.  
Pre-load was not applied. Without wetting samples.  
The average results are given for weft and warp direction of five samples  
Performed in the conditioned room (20 $\pm$ 2°C-65% $\pm$ 4).  
Dry ;

	<u>RESULT</u>	<u>REQUIREMENT</u>
Weft	82.8 N	$\geq$ 20N (Dry)
Warp	74.8 N	$\geq$ 20N (Dry)

### TENSILE STRENGTH; EN 29073-3:1996 (\*)

Instron 5969 (Load: 50 kN), Strip Method.  
Speed: 100 mm/min $\pm$ 10, Gauge length 200 mm.  
Pre-load was not applied. With wetting samples.  
The average results are given for weft and warp direction of five samples  
Performed in the conditioned room (20 $\pm$ 2°C-65% $\pm$ 4).  
Wet ;

	<u>RESULT</u>	<u>REQUIREMENT</u>
Weft	86.9 N	$\geq$ 20N (Wet)
Warp	71.5 N	$\geq$ 20N (Wet)

### BURSTING STRENGTH;; ISO 13938-1:1999

SDL ATLAS M229 tester. Test area: 30.5 mm diameter  
The average results are given of five samples.  
Performed in the conditioned room (20 $\pm$ 2°C-65% $\pm$ 4).  
Dry ;

	<u>RESULT</u>	<u>REQUIREMENT</u>
Height at Burst*	161.2 kPa	$\geq$ 40 kPa (Dry)
	15.5 mm	

## TEST RESULTS

TEST METHOD : EN 13795-1:2019

SURGICAL CLOTHING AND DRAPES –REQUIREMENTS AND TEST METHODS

ANNEX 1: SURGICAL CLOTHING AND DRAPES (\*);

**BURSTING STRENGTH;;** ISO 13938-1:1999

SDL ATLAS M229 tester. Test area: 30.5 mm diameter

The average results are given of five samples.

Performed in the conditioned room (20±2°C-65%±4).

Wet ;

**RESULT**

168.3 kPa

**REQUIREMENT**

≥ 40 kPa (Wet)

Height at Burst\*

14.3 mm